

"ReflecTech polymer film is a viable alternate to glass mirrors, offers comparable performance and durability, and is not susceptible to breakage as are glass mirrors."


Sargent & Lundy, LLC

ReflecTech

Mirror Film

ReflecTech® Mirror Film is a breakthrough technology for solar concentrators. It has the same reflectance as the glass mirrors used in previous generation systems but is lighter weight, lower cost and totally unbreakable, improving the economics of the solar concentrators of the future. ReflecTech has been proven to maintain its reflectance for decades, even in the harshest outdoor environments in the world.

SPECTRAL HEMISPHERICAL REFLECTANCE

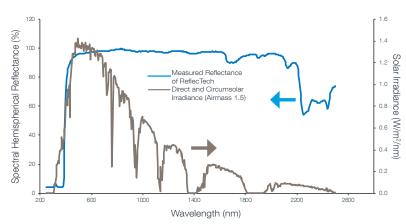

FEATURES

- High Reflectance
- Outdoor Weatherable
- Ultra-Lightweight
- Abrasion Resistant
- Commercially Prover
- Low Cost
- Self-Adhesive

ReflecTech Mirror Film has high reflectance in the wavelength range important for harnessing sunlight for thermal generation. Hemispherical reflectance is plotted on the left axis while the terrestrial irradiance of sunlight is plotted on the right axis, both as functions of wavelength. The specular reflectance is 94 %.



REFLECTECH® - BUILT ON COLLABORATION


ReflecTech was collaboratively developed by SkyFuel and the National Renewable Energy Laboratory (NREL) in the USA through an industry-leading public/private partnership. The result is a technology that is proven, reliable and guaranteed to improve the economics of solar concentrators. (US Patents 6,989,924 and 7,612,937)

ReflecTech uses pure silver to provide high specular reflectance and multiple layers of polymer films to protect against extreme outdoor environments including ultra-violet (UV) radiation and moisture. In addition, a tough, transparent coating protects the film against abrasion. The result is the most advanced reflective surface in the world.

EXCELLENT OUTDOOR WEATHERABILITY

ReflecTech has undergone extensive outdoor durability testing using the Ultra-Accelerated Weathering System (UAWS) at NREL. UAWS is an accelerated method to determine the long-term durability of a material to outdoor UV exposure. The UV portion of natural sunlight is concentrated 100X while sample exposure temperatures are maintained at 30 °C and 60 °C to accelerate degradation mechanisms. (2)

ReflecTech passed the 30-year milestone during its long-term UAWS durability test with almost no reflectance reduction.

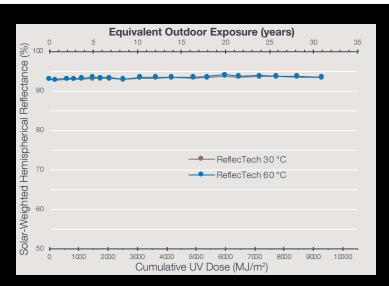

MOISTURE RESISTANCE

ReflecTech laminated to metal substrate panels were immersed in deionized water for 30 days at NREL. There was no sign of delamination at any layer interface. In addition, the cross-hatch tape peel test was also performed after immersion, and there was no loss of adhesion.



TESTED ABOVE AND BEYOND PASSING WITH FLYING COLORS

UV | Temperature | Moisture Test (ASTM G 155): 2 X UV | 30 °C & 60 °C | 5 % & 60 % Relative Humidity: 12,000 hours - pass

Outdoor Test (ASTM G 90) 5 X sunlight & hourly water spray: 7,500 hours - pass

Water Resistance Test (ASTM D 870) 30 days of immersion - pass

Cyclic Condensation (ASTM D 4587): 100 % relative humidity | 30 °C & 60 °C: 100 cycles - pass

Taber Abrasion (ASTM D 4060) | 30 cycles before and after weathering - pass Adhesion of Coating (ASTM D3359) | Cross hatch tape peel test before and after weathering - pass

Bending Test (ASTM D 522) @ 25 mm radius and above - pass

Hail Test (ASTM E 822) front and back, 1" diameter - pass

Falling Sand Abrasion (ASTM D 968) | 2 liters of 120 grit sand - pass


Thermal Cycling for Coatings (ASTM D 6944, Method B): 30 cycles - pass

Humidity Freeze Testing (IEC 62108, Section 10-8): -40 °C to 60 °C, ambient to 83 % relative humidity: 10 cycles - pass

Corrosion Testing, Salt Spray (Fog) (ASTM B 117): additional edge treatment, 500 hr - pass



Refectance after Abrasive Scrub Brush Test ©¹⁰⁰ 660 nm Specular Reflectance 12.5 mrad - 7 5 mrad 50 10000 20000 30000 40000 50000 60000 Number of Cycles

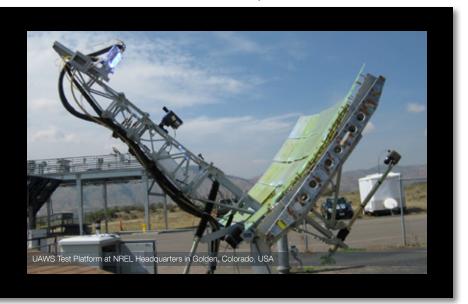


ABRASION RESISTANCE

Collaboratively developed(1) by SkyFuel and NREL, ReflecTech's unique tough, transparent coating maintains its optical efficiency even under abrasive circumstances, including regular cleaning maintenance and / or sand storms.

To simulate the most aggressive solar field mirror cleaning process, ASTM D2486(3) was performed with a BYK Model PB 5005 wet abrasion scrub tester. This test uses linearly actuated scrub brushes cycled in a back-andforth motion 37 times per minute across the surface of ReflecTech. The figure illustrates that no loss in specular reflectance occurred after over

50,000 back-andforth scrub brush cycles, simulating more than 50 years of routine cleaning.





CONCLUSION

After more than 15 years of continuous use in commercial applications, ReflecTech has become a proven and reliable reflective surface that is revolutionizing solar concentrators. It the most tested reflective surface in the Concentrated Solar Power industry and is guaranteed to last for decades in harsh outdoor environments. By surviving the extreme conditions found in typical solar projects such as heat, cold, humidity, wind, sand, hail and UV exposure, ReflecTech has demonstrated superior long-term performance over glass-based alternatives.

ReflecTech also enables innovative new solar concentrator designs that will dramatically reduce the cost of future solar projects and create a path towards a large scale-up of the CSP industry.

REFERENCES:

- (1) Gary Jorgensen, Randy Gee, and Michael DiGrazia, "Development and Testing of Abrasion Resistant Hard Coats for Polymer Film
- Reflectors", SolarPACES, 2010.
 H. K. Hardcastle, G. J. Jorgensen, and C. E. Bingham, "Ultra-Accelerated Weathering System I: Design and Functional Considerations", Natural and Artificial Aging of Polymers - 4th European Weathering Symposium; Reichert, T., Ed. Publication No. 11, Gesellschaft fur Umweltsimulation: Germany, 2009.
- (3) American Society of Testing and Materials (ASTM) Annual Book of Standards, ASTM International, West Conshohocken, PA, www.astm.org







ReflecTech® Specifications

PERFORMANCE CHARACTERISTICS

Specular Reflectance ⁽⁴⁾	94.0 %	At 12.5 mrad, 660 nm
Solar-Weighted Hemispherical Reflectance ⁽⁵⁾	92.5 %	ASTM G173

⁽⁴⁾ Measured on Devices & Services 15R Specular Reflectometer

PRODUCT / PHYSICAL CHARACTERISTICS

Nominal Thickness (mm)	0.1		
Coefficient of Thermal Expansion (cm / cm / °C)	5.5 x 10-5		ASTM E831
	Machine Direction	Transverse Direction	
Tensile Strength (MPa)	61	64	ASTM D882
Elongation at Break (%)	88	72	ASTM D882
Yield Strength at 2% Offset (MPa)	40	36	ASTM D882
Yield Elongation at 2% Offset (%)	4.7	4.6	ASTM D882
Modulus (MPa)	1430	1566	ASTM D882

APPLICATIONS CHARACTERISTICS

Adhesion to Aluminum ⁽⁶⁾ 180° Peel Strength (N / 25 mm)	10.0	ASTM D903
100 1 001 0ti origin (117 20 11111)		

⁽⁶⁾ Adhesion depends on the cleanliness and nature of the surface. The indicated values are for reference only.

OPERATION

Maximum Operating Temperature	60 °C	(140 °F)
Cleaning	Pressure wash with de-mineralized water	

For more information, contact:

info@SkyFuel.com

SkyFuel, Inc.
200 Union Blvd Suite 590, Lakewood, CO 80228, USA
+1 303.330.0276
www.SkyFuel.com | www.ReflecTechSolar.com



⁽⁵⁾ Integrated over Direct Normal air mass 1.5 solar spectrum